

Passive Fire Protection

Fire protection of structural elements

FIREPROOFING - BIOFIRE

Mortars

BIOFIRE

Fireproofing mortar for
passive fire protection
R15 to R240

Technical description

Gypsum based fireproofing sprayed with thermal insulation properties for passive fire protection in structural elements and compartmentation. BIOFIRE is composed of expanded lightweight aggregates (perlite and vermiculite), hydraulic binders, setting retarders and additives to improve mechanical application. It does not contain asbestos.

Field of application

BIOFIRE mortar is used for coating the structural elements of buildings for passive protection in case of fire, in order to maintain stability and the resistant capacity of these elements until the fire is extinguished and/or the building is evacuated.

Technical specifications

Base Gypsum

Colour White

Apparent density 600-760 Kg/m³

Hardened mortar density 850-900 Kg/m³

pH value 12

Adhesion $\geq 0.10^*$ N/mm² (Depending on the substrate)

Compression strength ≥ 2 N/mm²

Bend resistance ≥ 1 N/mm²
(after 28 days)

Theoretical performance 8.5 Kg/m²/cm

Application temperature Between 3 and 30 °C

Reaction to fire A1

Asbestos Asbestos free

Thermal conductivity 0.122 W/mK

Sound absorption(aw) 0.55(H). Class D Thickness 25 mm

Presentation 20 kg bags. 54 bags / pallet (1,120 Kg)

Application

BIOFIRE mortar is applied wet with a mixer and compressor type mortar spraying machine. It can be applied manually in small areas of application or for repairing damage.

Surface preparation

The surface must be dry and free of grease, dust and dirt. When working with absorbent surfaces it is recommended to spray the surface with water. When the surface does not provide sufficient guarantee of adherence, you must place a mesh or bonding bridge before spraying.

Mesh

No mesh required except when using the mortar on wood, pipes and on concrete (in some cases). It is also recommended for use in flanges of girders 500 mm or more in width, in pillars where only one side is sprayed, and square or rectangular metal profiles and pillars subject to high deformation.

Spraying

Mix the product with water in the spraying machine. Spray the previously cleaned surface until the exact thickness is obtained (maximum thickness per layer 30 mm).

Finish

Rough-finished mortar. If necessary, it can be smoothed. The finish can be painted.

Approvals and Certificates

BIOFIRE is CE Marked by the European Technical Assessment (ETA) 18/1087 issued by the ITeC (Institute of Construction Technology of Catalonia).

Solutions included in ETA 12/0005:

- Metallic structure according to EN 13381-4

Classified system up to R 240

- Concrete structure according to EN 13381-3

Classified system up to REI 240

- Mixed structure according to EN 13381-5

Classified system up to REI 240

- Wooden frame according to EN 1365-2

Classified system up to REI 180


- Ventilation ducts* according to EN 1366-1

Classified system up to EI 120

* Rectangular Ventilation duct in horizontal position with exterior fire

Also BIOFIRE mortar has been subjected to a variety of tests of harmonised European standards to determine its fire resistance in different systems.

- Wooden structure according to EN 1363-1

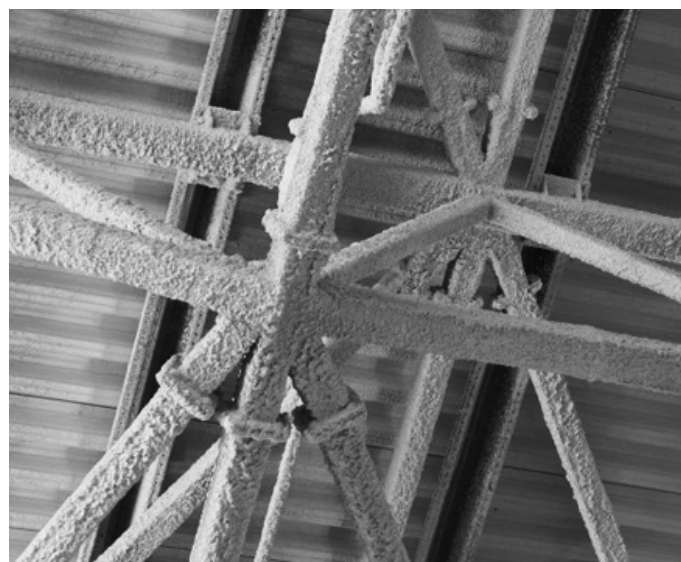

Classified system up to 120 minutes

- Ventilation ducts according to EN 1366-1

Classified system up to EI 180

- Concrete block wall according to EN 1364-1

Classified system up to EI 240

- BIOFIRE partition wall according to EN 1364-1

EI 120 classified system

- BIOFIRE ceiling according to EN 1364-2

EI 180 classified system

- Firewalls according to EN 1363-1 and “Fire resistance of intersection/party/cover barriers test” protocol.

Classified system up to EI 120.

Acoustic test

- Measurement of sound absorption according to UNE-EN ISO 354

Thermal conductivity test

- Thermal conductivity according to UNE-EN 12667



BIOFIRE THICKNESS TABLE

Fire Resistance Rating of Sections I/H								
A/V Section factor	Minimum thickness (mm) for a design temperature of 350 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	10	10	10	13	18	24	25	47
70	10	10	10	13	19	25	37	48
75	10	10	11	14	20	26	38	50
80	10	10	11	14	20	26	39	51
85	10	10	11	14	21	27	40	53
90	10	10	11	15	21	28	41	54
95	10	10	12	15	22	28	42	55
100	10	10	12	15	22	29	42	56
105	10	10	12	15	22	29	43	57
110	10	10	12	16	23	30	44	58
115	10	10	12	16	23	30	44	59
120	10	10	13	16	23	31	45	60
125	10	10	13	16	24	31	46	60
130	10	10	13	17	24	31	46	61
135	10	10	13	17	24	32	47	62
140	10	10	13	17	25	32	47	62
145	10	10	13	17	25	32	48	63
150	10	10	13	17	25	33	48	-
155	10	10	14	17	25	33	49	-
160	10	10	14	18	25	33	49	-
165	10	10	14	18	26	34	49	-
170	10	10	14	18	26	34	50	-
175	10	10	14	18	26	34	50	-
180	10	10	14	18	26	34	50	-
185	10	10	14	18	26	35	51	-
190	10	10	14	18	27	35	51	-
195	10	10	14	18	27	35	51	-
200	10	10	14	19	27	35	52	-
205	10	10	14	19	27	35	52	-
210	10	10	15	19	27	35	52	-
215	10	10	15	19	27	36	53	-
220	10	10	15	19	27	36	53	-
225	10	11	15	19	28	36	53	-
230	10	11	15	19	28	36	53	-
235	10	11	15	19	28	36	53	-
240	10	10	15	19	28	36	54	-
245	10	11	15	19	28	37	54	-
250	10	11	15	19	28	37	54	-
255	10	11	15	19	28	37	54	-
260	10	11	15	20	28	37	54	-
265	10	11	15	20	28	37	55	-
270	10	11	15	20	28	37	55	-
275	10	11	15	20	29	37	55	-
280	10	11	15	20	29	37	55	-
285	10	11	15	20	29	38	55	-
290	10	11	15	20	29	38	55	-
295	10	11	16	20	29	38	55	-

ETA 18/1087

BIOFIRE THICKNESS TABLE

Fire Resistance Rating of Sections I/H								
A/V Section factor	Minimum thickness (mm) for a design temperature of 400 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	10	10	10	11	16	22	32	43
70	10	10	10	11	17	22	34	45
75	10	10	10	12	18	23	35	46
80	10	10	10	12	18	24	36	47
85	10	10	10	13	19	25	37	49
90	10	10	10	13	19	25	37	50
95	10	10	10	13	20	26	38	51
100	10	10	10	14	20	26	39	52
105	10	10	11	14	20	27	40	53
110	10	10	11	14	21	27	40	54
115	10	10	11	14	21	28	41	54
120	10	10	11	15	21	28	42	55
125	10	10	11	15	22	29	42	56
130	10	10	12	15	22	29	43	57
135	10	10	12	15	22	29	43	57
140	10	10	12	15	22	30	44	58
145	10	10	12	16	23	30	44	59
150	10	10	12	16	23	30	45	59
155	10	10	12	16	23	31	45	60
160	10	10	12	16	23	31	46	60
165	10	10	12	16	24	31	46	61
170	10	10	13	16	24	31	46	61
175	10	10	13	16	24	31	47	62
180	10	10	13	17	24	31	47	62
185	10	10	13	17	24	32	47	63
190	10	10	13	17	25	32	48	63
195	10	10	13	17	25	32	48	63
200	10	10	13	17	25	33	48	-
205	10	10	13	17	25	33	48	-
210	10	10	13	17	25	33	49	-
215	10	10	13	17	25	33	49	-
220	10	10	13	17	25	33	49	-
225	10	10	14	18	25	33	49	-
230	10	10	14	18	26	34	50	-
235	10	10	14	18	26	34	50	-
240	10	10	14	18	26	34	50	-
245	10	10	14	18	26	34	50	-
250	10	10	11	18	26	34	51	-
255	10	10	14	18	26	34	51	-
260	10	10	14	18	26	34	51	-
265	10	10	14	18	26	35	51	-
270	10	10	14	18	26	35	51	-
275	10	10	14	18	27	35	51	-
280	10	10	14	18	27	35	52	-
285	10	10	14	18	27	35	52	-
290	10	10	14	18	27	35	52	-
295	10	10	14	18	27	35	52	-

Fire Resistance Rating of Sections I/H								
A/V Section Factor	Minimum thickness (mm) for a design temperature of 450 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	10	10	10	10	14	19	29	39
70	10	10	10	10	15	20	30	40
75	10	10	10	10	16	21	31	42
80	10	10	10	11	16	22	32	43
85	10	10	10	11	17	22	33	45
90	10	10	10	11	17	23	34	46
95	10	10	10	12	17	23	35	47
100	10	10	10	12	18	24	36	48
105	10	10	10	12	18	24	36	49
110	10	10	10	12	19	25	37	49
115	10	10	10	13	19	25	38	50
120	10	10	10	13	19	26	38	51
125	10	10	10	13	20	26	39	52
130	10	10	10	13	20	26	39	52
135	10	10	10	14	20	27	40	53
140	10	10	10	14	20	27	40	54
145	10	10	11	14	21	27	41	54
150	10	10	11	14	21	28	41	55
155	10	10	11	14	21	28	42	55
160	10	10	11	14	21	28	42	56
165	10	10	11	15	22	29	42	56
170	10	10	11	15	22	29	42	56
175	10	10	11	15	22	29	43	57
180	10	10	11	15	22	29	43	58
185	10	10	12	15	22	29	44	58
190	10	10	12	15	22	30	44	58
195	10	10	12	15	23	30	44	59
200	10	10	12	15	23	30	45	59
205	10	10	12	16	23	30	45	60
210	10	10	12	16	23	30	45	60
215	10	10	12	16	23	31	45	60
220	10	10	12	16	23	31	46	60
225	10	10	12	16	23	31	46	61
230	10	10	12	16	24	31	46	61
235	10	10	12	16	24	31	46	61
240	10	10	12	16	24	31	46	62
245	10	10	13	16	24	32	47	62
250	10	10	13	16	24	32	47	62
255	10	10	13	16	24	32	47	62
260	10	10	13	17	24	32	47	63
265	10	10	13	17	24	32	47	63
270	10	10	13	17	24	32	48	63
275	10	10	13	17	25	32	48	63
280	10	10	13	17	25	32	48	63
285	10	10	13	17	25	32	48	-
290	10	10	13	17	25	33	48	-
295	10	10	13	17	25	33	48	-

ETA 18/1087

BIOFIRE THICKNESS TABLE

Fire Resistance Rating of Sections I/H								
A/V Section factor	Minimum thickness (mm) for a design temperature of 500 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	10	10	10	10	13	18	27	37
70	10	10	10	10	14	19	28	38
75	10	10	10	10	14	19	30	40
80	10	10	10	10	15	20	31	41
85	10	10	10	10	15	21	31	42
90	10	10	10	10	16	21	32	43
95	10	10	10	11	16	22	33	44
100	10	10	10	11	17	22	34	45
105	10	10	10	11	17	23	35	46
110	10	10	10	11	17	23	35	47
115	10	10	10	12	18	24	36	48
120	10	10	10	12	18	24	36	49
125	10	10	10	12	18	25	37	49
130	10	10	10	12	19	25	38	50
135	10	10	10	13	19	25	38	51
140	10	10	10	13	19	26	38	51
145	10	10	10	13	19	26	39	52
150	10	10	10	13	20	26	39	52
155	10	10	10	13	20	27	40	53
160	10	10	10	13	20	27	40	54
165	10	10	10	14	20	27	41	54
170	10	10	10	14	21	27	41	54
175	10	10	11	14	21	28	41	55
180	10	10	11	14	21	28	42	55
185	10	10	11	14	21	28	42	56
190	10	10	11	14	21	28	42	56
195	10	10	11	14	21	28	42	56
200	10	10	11	15	22	29	43	57
205	10	10	11	15	22	29	43	57
210	10	10	11	15	22	29	43	58
215	10	10	11	15	22	29	44	58
220	10	10	11	15	22	29	44	58
225	10	10	11	15	22	30	44	58
230	10	10	12	15	22	30	44	59
235	10	10	12	15	23	30	44	59
240	10	10	12	15	23	30	45	59
245	10	10	12	15	23	30	45	60
250	10	10	12	16	23	30	45	60
255	10	10	12	16	23	30	45	60
260	10	10	12	16	23	31	45	60
265	10	10	12	16	23	31	46	61
270	10	10	12	16	23	31	46	61
275	10	10	12	16	23	31	46	61
280	10	10	12	16	23	31	46	61
285	10	10	12	16	24	31	46	61
290	10	10	12	16	24	31	46	62
295	10	10	12	16	24	31	47	62

Fire Resistance Rating of Sections I/H								
A/V Section factor	Minimum thickness (mm) for a design temperature of 550 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	10	10	10	10	12	17	26	36
70	10	10	10	10	13	18	27	37
75	10	10	10	10	13	18	28	38
80	10	10	10	10	14	19	29	40
85	10	10	10	10	14	20	30	41
90	10	10	10	10	15	20	31	42
95	10	10	10	10	15	21	32	43
100	10	10	10	10	16	21	33	44
105	10	10	10	10	16	22	33	45
110	10	10	10	11	17	22	34	46
115	10	10	10	11	17	23	35	47
120	10	10	10	11	17	23	35	47
125	10	10	10	11	18	24	36	48
130	10	10	10	12	18	24	36	49
135	10	10	10	12	18	24	37	50
140	10	10	10	12	18	25	37	50
145	10	10	10	12	19	25	38	51
150	10	10	10	12	19	25	38	51
155	10	10	10	13	19	26	39	52
160	10	10	10	13	19	26	39	52
165	10	10	10	13	20	26	40	53
170	10	10	10	13	20	27	40	53
175	10	10	10	13	20	27	40	54
180	10	10	10	13	20	27	41	54
185	10	10	10	14	20	27	41	55
190	10	10	10	14	21	27	41	55
195	10	10	10	14	21	28	42	55
200	10	10	10	14	21	28	42	56
205	10	10	11	14	21	28	42	56
210	10	10	11	14	21	28	42	56
215	10	10	11	14	21	28	43	57
220	10	10	11	14	22	29	43	57
225	10	10	11	15	22	29	43	57
230	10	10	11	15	22	29	43	58
235	10	10	11	15	22	29	44	58
240	10	10	11	15	22	29	44	58
245	10	10	11	15	22	29	44	59
250	10	10	11	15	22	30	44	59
255	10	10	11	15	22	30	44	59
260	10	10	11	15	22	30	45	59
265	10	10	12	15	23	30	45	59
270	10	10	12	15	23	30	45	60
275	10	10	12	15	23	30	45	60
280	10	10	12	15	23	30	45	60
285	10	10	12	15	23	30	45	60
290	10	10	12	16	23	31	46	61
295	10	10	12	16	23	31	46	61

ETA 18/1087

BIOFIRE THICKNESS TABLE

Fire Resistance Rating of Sections I/H								
A/V Section factor	Minimum thickness (mm) for a design temperature of 600 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	10	10	10	10	11	16	25	34
70	10	10	10	10	12	16	26	36
75	10	10	10	10	12	17	27	37
80	10	10	10	10	13	18	28	38
85	10	10	10	10	13	19	29	40
90	10	10	10	10	14	19	30	41
95	10	10	10	10	14	20	31	42
100	10	10	10	10	15	20	32	43
105	10	10	10	10	15	21	32	44
110	10	10	10	10	16	21	33	45
115	10	10	10	10	16	22	34	45
120	10	10	10	10	16	22	34	46
125	10	10	10	11	17	23	35	47
130	10	10	10	11	17	23	35	48
135	10	10	10	11	17	24	36	48
140	10	10	10	11	18	24	36	49
145	10	10	10	12	18	24	37	50
150	10	10	10	12	18	25	37	50
155	10	10	10	12	18	25	38	51
160	10	10	10	12	19	25	38	51
165	10	10	10	12	19	25	39	52
170	10	10	10	12	19	26	39	52
175	10	10	10	13	19	26	39	53
180	10	10	10	13	20	26	40	53
185	10	10	10	13	20	26	40	53
190	10	10	10	13	20	27	40	54
195	10	10	10	13	20	27	41	54
200	10	10	10	13	20	27	41	56
205	10	10	10	13	20	27	41	56
210	10	10	10	14	21	27	41	55
215	10	10	10	14	21	28	42	56
220	10	10	10	14	21	28	42	56
225	10	10	10	14	21	28	42	56
230	10	10	10	14	21	28	42	57
235	10	10	11	14	21	28	43	57
240	10	10	11	14	21	29	43	57
245	10	10	11	14	21	29	43	57
250	10	10	11	14	22	29	43	58
255	10	10	11	14	22	29	43	58
260	10	10	11	15	22	29	44	58
265	10	10	11	15	22	29	44	58
270	10	10	11	15	22	29	44	59
275	10	10	11	15	22	29	44	59
280	10	10	11	15	22	30	44	59
285	10	10	11	15	22	30	44	59
290	10	10	11	15	22	30	45	59
295	10	10	11	15	23	30	45	60

Fire Resistance Rating of Hollow Sections								
A/V Section factor	Minimum thickness (mm) for a design temperature of 350 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	11	11	11	14	19	26	27	50
70	11	11	11	14	20	27	40	51
75	11	11	12	15	22	28	41	54
80	11	11	12	15	22	28	42	55
85	11	11	12	15	23	29	43	58
90	11	11	12	16	23	31	45	59
95	11	11	13	16	24	31	46	60
100	11	11	13	17	24	32	46	62
105	11	11	13	17	24	32	48	63
110	11	11	13	18	26	33	49	-
115	11	11	13	18	26	33	49	-
120	11	11	15	18	26	35	50	-
125	11	11	15	18	27	35	52	-
130	11	11	15	19	27	35	52	-
135	11	11	15	19	27	36	53	-
140	11	11	15	19	29	36	54	-
145	11	11	15	19	29	37	55	-
150	12	12	15	20	29	38	55	-
155	12	12	16	20	29	38	57	-
160	12	12	16	21	29	38	57	-
165	12	12	16	21	30	40	57	-
170	12	12	16	21	30	40	59	-
175	12	12	16	21	31	40	59	-
180	12	12	16	21	31	40	59	-
185	12	12	17	21	31	40	59	-
190	12	12	17	21	32	42	61	-
195	12	12	17	22	32	42	61	-
200	12	12	17	23	32	42	62	-
205	12	12	17	23	33	42	63	-
210	12	12	18	23	33	42	63	-
215	12	12	18	23	33	44	-	-
220	12	12	18	23	33	44	-	-
225	12	13	18	23	34	44	-	-
230	12	14	18	23	34	44	-	-
235	12	14	19	23	35	44	-	-
240	12	14	19	24	35	45	-	-
245	12	14	19	24	35	46	-	-
250	13	14	19	24	35	46	-	-
255	13	14	19	24	35	46	-	-
260	13	14	19	25	35	46	-	-
265	13	14	19	25	35	46	-	-
270	13	14	19	25	35	46	-	-
275	13	14	19	25	36	46	-	-
280	13	14	19	25	36	46	-	-
285	13	14	19	25	36	48	-	-
290	13	14	19	25	36	48	-	-
295	13	14	20	25	36	48	-	-

ETA 18/1087

BIOFIRE THICKNESS TABLE

Fire Resistance Rating of Hollow Sections								
A/V Section factor	Minimum thickness (mm) for a design temperature of 400 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	11	11	11	12	17	23	34	46
70	11	11	11	12	18	24	36	48
75	11	11	11	13	19	25	38	49
80	11	11	11	13	19	26	39	51
85	11	11	11	14	21	27	40	53
90	11	11	11	14	21	27	40	55
95	11	11	11	14	22	28	42	56
100	11	11	11	15	22	29	43	57
105	11	11	12	15	22	30	44	59
110	11	11	12	16	23	30	44	60
115	11	11	12	16	23	31	46	60
120	11	11	12	17	24	31	47	62
125	11	11	12	17	25	33	47	63
130	11	11	14	17	25	33	49	-
135	11	11	14	17	25	33	49	-
140	11	11	14	17	25	34	50	-
145	11	11	14	18	26	34	50	-
150	12	12	14	18	26	35	52	-
155	12	12	14	18	27	36	52	-
160	12	12	14	19	27	36	53	-
165	12	12	14	19	28	36	54	-
170	12	12	15	19	28	36	54	-
175	12	12	15	19	28	38	55	-
180	12	12	15	20	28	38	55	-
185	12	12	15	20	28	38	56	-
190	12	12	15	20	30	38	57	-
195	12	12	16	20	30	38	57	-
200	12	12	16	20	30	40	58	-
205	12	12	16	20	30	40	58	-
210	12	12	16	20	30	40	58	-
215	12	12	16	21	30	40	59	-
220	12	12	16	21	31	40	60	-
225	12	12	17	22	31	40	60	-
230	12	12	17	22	32	42	62	-
235	12	12	17	22	32	42	62	-
240	12	12	17	22	32	42	62	-
245	12	12	17	22	32	42	62	-
250	13	13	18	23	33	43	-	-
255	13	13	18	23	33	43	-	-
260	13	13	18	23	33	43	-	-
265	13	13	18	23	33	44	-	-
270	13	13	18	23	33	44	-	-
275	13	13	18	23	34	44	-	-
280	13	13	18	23	34	44	-	-
285	13	13	18	23	34	44	-	-
290	13	13	18	23	34	44	-	-
295	13	13	18	23	34	44	-	-

Fire Resistance Rating of Hollow Sections								
A/V Section factor	Minimum thickness (mm) for a design temperature of 450 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	11	11	11	11	15	20	31	42
70	11	11	11	11	16	21	32	44
75	11	11	11	11	17	23	33	45
80	11	11	11	12	17	24	35	46
85	11	11	11	12	18	24	36	49
90	11	11	11	12	19	25	37	50
95	11	11	11	13	19	25	38	51
100	11	11	11	13	20	26	40	53
105	11	11	11	13	20	27	40	54
110	11	11	11	13	21	28	41	54
115	11	11	11	14	21	28	42	56
120	11	11	11	15	21	29	43	57
125	11	11	11	15	23	29	44	59
130	11	11	11	15	23	29	44	59
135	11	11	11	16	23	31	45	60
140	11	11	11	16	23	31	46	62
145	11	11	13	16	24	31	47	62
150	12	12	13	16	24	32	47	63
155	12	12	13	16	24	32	49	-
160	12	12	13	16	24	32	49	-
165	12	12	13	17	26	34	49	-
170	12	12	13	18	26	34	50	-
175	12	12	13	18	26	34	51	-
180	12	12	13	18	26	34	51	-
185	12	12	14	18	26	34	52	-
190	12	12	14	18	16	36	52	-
195	12	12	14	18	27	36	53	-
200	12	12	14	18	28	36	54	-
205	12	12	14	19	28	36	54	-
210	12	12	15	19	28	36	54	-
215	12	12	15	19	28	38	55	-
220	12	12	15	20	28	38	56	-
225	12	12	15	20	28	38	56	-
230	12	12	15	20	30	38	57	-
235	12	12	15	20	30	38	57	-
240	12	12	15	20	30	38	57	-
245	12	12	16	20	30	40	59	-
250	13	13	16	20	30	40	59	-
255	13	13	16	20	30	40	59	-
260	13	13	16	21	30	40	59	-
265	13	13	16	21	30	40	59	-
270	13	13	16	21	30	40	60	-
275	13	13	16	21	31	40	60	-
280	13	13	16	21	31	40	60	-
285	13	13	16	21	31	40	60	-
290	13	13	16	21	31	41	60	-
295	13	13	16	21	31	41	60	-

ETA 18/1087

BIOFIRE THICKNESS TABLE

Fire Resistance Rating of Hollow Sections								
A/V Section factor	Minimum thickness (mm) for a design temperature of 500 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	11	11	11	11	14	19	29	39
70	11	11	11	11	15	20	30	41
75	11	11	11	11	15	20	32	43
80	11	11	11	11	16	22	33	44
85	11	11	11	11	16	23	34	46
90	11	11	11	11	17	23	35	47
95	11	11	11	12	18	24	36	48
100	11	11	11	12	19	24	37	50
105	11	11	11	12	19	25	39	51
110	11	11	11	12	19	26	39	52
115	11	11	11	13	20	27	40	54
120	11	11	11	13	20	27	40	55
125	11	11	11	14	20	28	42	55
130	11	11	11	14	21	28	43	57
135	11	11	11	15	22	28	43	58
140	11	11	11	15	22	30	43	58
145	11	11	11	15	22	30	45	60
150	12	12	12	15	23	30	45	60
155	12	12	12	15	23	31	46	61
160	12	12	12	15	23	31	46	63
165	12	12	12	16	23	31	48	63
170	12	12	12	16	25	32	48	63
175	12	12	13	16	25	33	48	-
180	12	12	13	17	25	33	50	-
185	12	12	13	17	25	33	50	-
190	12	12	13	17	25	33	50	-
195	12	12	13	17	25	33	50	-
200	12	12	13	18	26	35	52	-
205	12	12	13	18	27	35	52	-
210	12	12	13	18	27	35	52	-
215	12	12	13	18	27	35	53	-
220	12	12	13	18	27	35	54	-
225	12	12	13	18	27	37	54	-
230	12	12	15	18	27	37	54	-
235	12	12	15	19	28	37	54	-
240	12	12	15	19	29	37	56	-
245	12	12	15	19	29	37	56	-
250	13	13	15	20	29	38	56	-
255	13	13	15	20	29	38	56	-
260	13	13	15	20	29	39	56	-
265	13	13	15	20	29	39	58	-
270	13	13	15	20	29	39	58	-
275	13	13	15	20	29	39	58	-
280	13	13	15	20	29	39	58	-
285	13	13	15	20	30	39	58	-
290	13	13	15	20	30	39	58	-
295	13	13	15	20	30	39	59	-

Fire Resistance Rating of Hollow Sections								
A/V Section factor	Minimum thickness (mm) for a design temperature of 550 °C							
(Am/V (m ³))	R15	R30	R45	R60	R90	R120	R180	R240
65	11	11	11	11	13	18	28	38
70	11	11	11	11	14	19	29	40
75	11	11	11	11	14	19	30	41
80	11	11	11	11	15	21	31	43
85	11	11	11	12	15	22	33	44
90	11	11	11	11	16	22	34	46
95	11	11	11	11	16	23	35	47
100	11	11	11	11	16	23	35	47
105	11	11	11	11	18	24	36	50
110	11	11	11	12	19	24	38	51
115	11	11	11	12	19	26	39	52
120	11	11	11	12	19	26	39	53
125	11	11	11	12	20	27	41	54
130	11	11	11	14	20	27	41	55
135	11	11	11	14	20	27	42	57
140	11	11	11	14	21	29	42	57
145	11	11	11	14	22	29	44	58
150	12	12	12	14	22	29	44	59
155	12	12	12	15	22	30	45	60
160	12	12	12	15	22	30	45	60
165	12	12	12	15	23	30	47	62
170	12	12	12	15	23	32	47	62
175	12	12	12	15	24	32	47	-
180	12	12	12	15	24	32	48	-
185	12	12	12	17	24	32	49	-
190	12	12	12	17	25	32	49	-
195	12	12	12	17	25	33	50	-
200	12	12	12	17	25	34	50	-
205	12	12	13	17	25	34	51	-
210	12	12	13	17	25	34	51	-
215	12	12	13	17	26	34	52	-
220	12	12	13	17	27	35	52	-
225	12	12	13	18	27	36	53	-
230	12	12	14	18	27	36	53	-
235	12	12	14	19	27	36	54	-
240	12	12	14	19	27	36	55	-
245	12	12	14	19	27	36	55	-
250	13	13	14	19	28	38	55	-
255	13	13	14	19	28	38	55	-
260	13	13	14	19	28	38	56	-
265	13	13	15	9	29	38	56	-
270	13	13	15	19	29	38	56	-
275	13	13	15	19	29	38	56	-
280	13	13	15	19	29	38	56	-
285	13	13	15	19	29	38	56	-
290	13	13	15	20	29	39	58	-
295	13	13	15	20	29	39	58	-



ETA 18/1087

BIOFIRE THICKNESS TABLE

Fire Resistance Rating of Hollow Sections								
A/V Section factor	Minimum thickness (mm) for a design temperature of 600 °C							
(Am/V (m ⁻¹))	R15	R30	R45	R60	R90	R120	R180	R240
65	11	11	11	11	12	17	27	36
70	11	11	11	11	13	17	28	39
75	11	11	11	11	13	18	29	40
80	11	11	11	11	14	19	30	41
85	11	11	11	11	14	21	31	43
90	11	11	11	11	15	21	33	45
95	11	11	11	11	15	22	34	46
100	11	11	11	11	17	22	35	47
105	11	11	11	11	17	23	35	49
110	11	11	11	11	18	23	37	50
115	11	11	11	11	18	25	38	50
120	11	11	11	11	18	25	38	52
125	11	11	11	12	19	26	39	53
130	11	11	11	12	19	26	40	54
135	11	11	11	12	19	27	41	54
140	11	11	11	13	21	27	41	56
145	11	11	11	14	21	27	42	57
150	12	12	12	14	21	29	43	58
155	12	12	12	14	21	29	44	59
160	12	12	12	14	22	29	44	59
165	12	12	12	14	22	29	45	61
170	12	12	12	14	22	30	46	61
175	12	12	12	15	22	31	46	62
180	12	12	12	15	24	31	47	63
185	12	12	12	15	24	31	47	63
190	12	12	12	15	24	32	48	-
195	12	12	12	16	24	32	49	-
200	12	12	12	16	24	32	49	-
205	12	12	12	16	24	33	49	-
210	12	12	12	17	25	33	50	-
215	12	12	12	17	26	34	51	-
220	12	12	12	17	26	34	51	-
225	12	12	12	17	26	34	51	-
230	12	12	12	17	26	34	52	-
235	12	12	14	17	26	35	53	-
240	12	12	14	17	26	36	53	-
245	12	12	14	17	26	36	54	-
250	13	13	14	18	28	36	54	-
255	13	13	14	18	28	36	54	-
260	13	13	14	19	28	36	55	-
265	13	13	14	19	28	36	55	-
270	13	13	14	19	28	36	55	-
275	13	13	14	19	28	36	55	-
280	13	13	14	19	28	38	55	-
285	13	13	14	19	28	38	55	-
290	13	13	14	19	28	38	56	-
295	13	13	14	19	29	38	56	-

BIOFIRE

Protection of mixed concrete deck floors, concrete slabs, bi-axial ribbed floors and concrete beams R30 to R120 REI 30 to 240

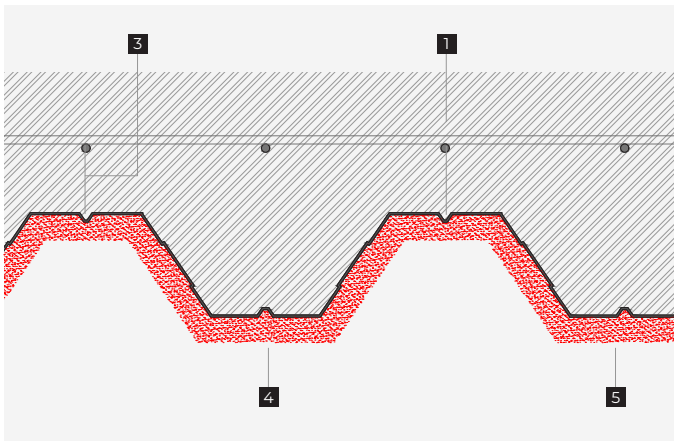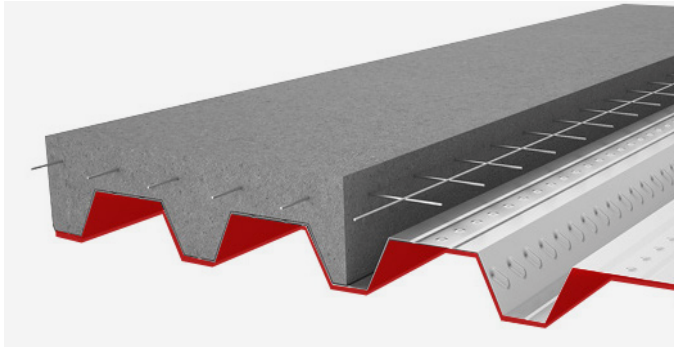

- 1 | Height of slab (h_s)
- 2 | Reinforcement
- 3 | Concrete topcoat between the bottom reinforcement and the side exposed to fire (a)
- 4 | Galvanized steel plate
- 5 | BIOFIRE mortar

Protection of mixed concrete deck floors

The fire resistance of a mixed concrete slab is determined by the minimum height of the slab (h_s) and the thickness of concrete topcoat between the bottom reinforcement and the side exposed to fire (a) according to table C.4 Mass concrete slabs, in the CTE DB SI annex C. If there is no reinforcement, the decking plate is used to calculate this. By coating the mixed concrete decking slab using sprayed-on BIOFIRE mortar, we can increase fire resistance to REI-180 minutes. APPLICATION: Mechanical application using wet mortar spraying machines with screw pumps. SURFACE PREPARATION: The galvanized steel plate substrate must be clean of grease, dust, and dirt. No bonding agent or anchor mesh is necessary. THICKNESS CALCULATION: BIOFIRE mortar acts as additional thickness of equivalent concrete. BIOFIRE mortar is tested under ENV 13381-5 - ETA 18/1087 the following procedure in a mixed concrete decking slab, the following process must be followed: Define the REI of the slab as required in current regulations. Determine the minimum height of the slab (h_s) and the distance between the bottom reinforcement and the face exposed to fire (a). Calculate the additional thickness of concrete for the slab to achieve the REI required by regulation using Table C.4 Solid slabs, of Annex C of the Technical Building Code (CTE). The table determines the resistance of the element based on the minimum height of the slab and the distance between the centre line of the reinforcement and the face exposed to fire. Calculate the thickness of BIOFIRE mortar needed and equivalent to the concrete using table (1) equivalent thickness of concrete.

C.4 solid slabs, in Annex C of the Technical Building Code		
Fire resistance	Minimum thickness hmin (mm)	Minimum equivalent distance to centre line am (mm)
REI 30	60 mm	10 mm
REI 60	80 mm	20 mm
REI 90	100 mm	25 mm
REI 120	120 mm	35 mm
REI 180	150 mm	50 mm
REI 240	175 mm	60 mm

For protection of concrete slab, bi-axial ribbed floor, one-way slabs with ceramic, concrete in-fill elements and concrete beams, contact TRIA Technical department.



TRIA BIOFIRE - FIREPROOFING



TRIA
Serviços, Materiais
e Equipamentos, SA.

Parque Ind. Manuel
Lourenço Ferreira - Lt. 43
3450-232 Mortágua -
Portugal

+351 231 927 480
geral@tria.pt